


COPOLYMERIZATIONS OF LONG SIDE CHAIN DI-N-ALKYL ITACONATES AND METHYL N-ALKYL ITACONATES WITH STYRENE: DETERMINATION OF MONOMERS REACTIVITY RATIOS BY NMR

Elizabeth Rangel-Rangel<sup>1</sup>, Carlos Torres<sup>1</sup>, Luís Rincón<sup>2</sup>, Sonia Koteich-Khatib<sup>3</sup>,  
Francisco López-Carrasquero<sup>1</sup>.\*

1: Grupo de Polímeros; 2: Grupo de Procesos Dinámicos en Química; 3: Laboratorio de Resonancia Magnética Nuclear  
Departamento de Química, Facultad de Ciencias, Universidad de Los Andes. 5101, Mérida, Venezuela.

\* email: flopezc@ula.ve

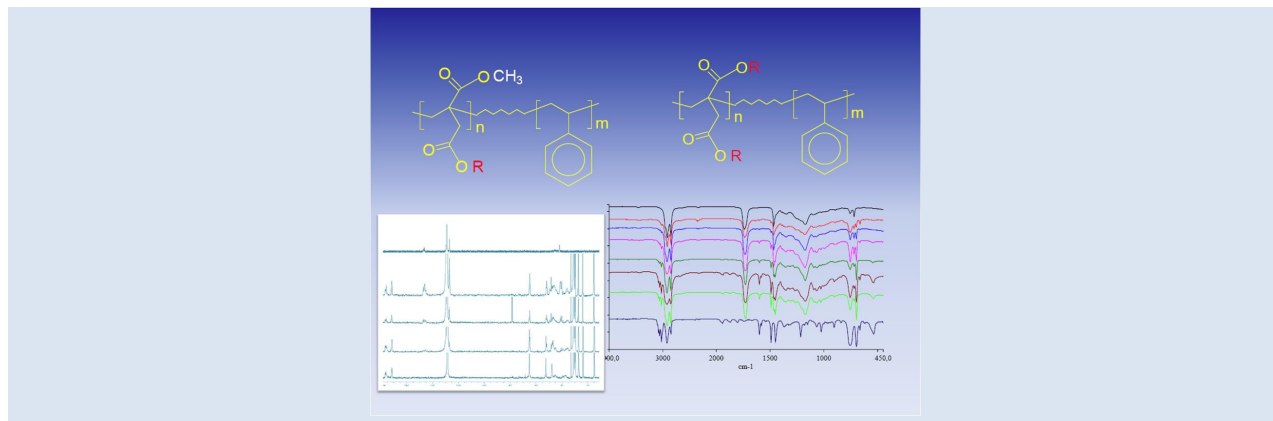

## ABSTRACT

Low yields copolymerization of styrene (S) with di-n-alkylitaconates (DI-n) and methyl n-alkylitaconates (MeI-n) with alkyl side chain of 12, 14, 16, 18 and 22 carbon atoms were carried out in bulk via radical at 60°C with AIBN as initiator. The copolymers chemical structure was characterized by FTIR and <sup>1</sup>H and <sup>13</sup>C-NMR, and the composition was determined by <sup>1</sup>H-NMR. The NMR studies indicate that the copolymers are random, but with some tendency to alternation. The monomers reactivity ratios between the styrene and itaconates in the copolymerization ( $r_i$ ) were calculated by the Fineman-Ross (FR), Kelen Tüdös (KT) methods and a modification of the last one. The obtained values of  $r_1$ (DI) and  $r_2$ (S) in the copolymerization among DI-n with  $n = 12, 14$  and  $16$  with S were in the range of 0.22 to 0.28 for DI-n and 0.19 to 0.39 for S. Whereas for DI-n with  $n = 18$  and  $22$  the values are in the order of 0.42-0.50 and 0.37-0.47 respectively. For the copolymer series derivatives of MeI-n the values were between 0.01-0.41 for the itaconate and 0.44-0.97 for S.

**Keywords:** n-alkylitaconate, styrene, copolymerization, reactivity ratios

## COPOLIMERIZACIÓN DE DIITACONATOS Y METIL ITACONATOS DE N-ALQUILO DE CADENAS LATERALES LARGAS CON ESTIRENO: DETERMINACIÓN DE LAS RELACIONES DE REACTIVIDAD DE LOS MONÓMEROS POR RMN.

## RESUMEN

La copolimerización a bajos grados de conversión de estireno (S) con di-n-alkylitaconatos (DI-n) y de metil-n-alkyl itaconatos (MeI-n) con cadenas laterales de 12, 14, 16, 18 y 22 átomos de carbono se llevó a cabo por vía radical, en masa a 60°C y empleando AIBN como iniciador. La estructura química de los copolímeros se caracterizó por FTIR y RMN-<sup>1</sup>H y <sup>13</sup>C y la composición se determinó por RMN-<sup>1</sup>H. Los estudios de RMN indican que los copolímeros son estadísticos pero con cierta tendencia a la alternancia. Las relaciones de reactividad ( $r_i$ ) entre el estireno e itaconatos se calcularon mediante los métodos de Fineman-Ross (FR), Kelen Tüdös (KT) y una modificación esta última. Los valores obtenidos de  $r_1$ (DI) y  $r_2$ (S) en la copolimerización entre los DI-n con  $n = 12, 14$  y  $16$  con S estuvieron en el rango de 0.22 a 0.28 para DI-n y 0.19 a 0.39 para S, mientras que los valores encontrados para los DI-n con  $n = 18$  y  $22$  son del orden de 0.42-0.50 y 0.37-0.47 para el itaconato y estireno respectivamente. Para la serie de MeI-n, los valores oscilaron entre 0.01 hasta 0.41 para los itaconatos y 0.44 a 0.97 para el S.

**Palabras Claves:** n-alkylitaconatos, estireno, copolimerización, relaciones de reactividad

## 1. INTRODUCTION

Polyitaconates have been widely studied for decades possibly due to its structural similarity with the polyacrylates and polymethacrylates and by the low cost of the itaconic acid, substance from which the itaconates are obtained [1]. Many of these researches have been oriented to the study of the amorphous state and properties in dissolution [1-4], while others have focused in the study of their thermal degradation [5-9]. A more recent studies carried out with a series of poly(mono *n*-alkyl itaconate)s, poly(methyl *n*-alkyl itaconate)s and poly(di-*n*-alkyl itaconate)s with *n* = 12, 14, 16, 18 and 22 showed that from certain size, the *n*-alkyl side-chains are able to crystallize [10, 11].

The copolymerization of itaconates with vinyl monomers had also received some attention, for example, the copolymerization of methyl and butyl diitaconates with vinyl monomers as styrene and methyl methacrylate had been studied [12-19]. On the other hand, a long side chain series of mono *n*-alkyl itaconates [20] and the *n*-hexadecyl diitaconate [21] were copolymerized with styrene. For these copolymers the *n*-alkyl side chains were able to crystallize depending on both the copolymer composition and their length. Even though, there have been a considerable number of studies on the copolymerization of itaconate with vinyl monomers, only very few of them report on the reactivity ratios between monomers. So for example, the reactivity ratios in the copolymerization of styrene with mono *n*-alkyl itaconates with *n* = 6-12 [22, 23] and 1-methyl itaconate derivatives [24, 25] were described. The possibility of copolymerized itaconates with vinyl monomers would improve the properties of these materials and the formation of gels would also enhance the application of these materials making them good candidates to be used in the manufacture of purification devices such as filters and membranes or as filler for analytical columns [26].

Since the little knowledge about the reactivity ratios of the copolymerization between styrene and *n*-alkyl itaconates, the possible influence of proportion and how the monomers are distributed in the copolymer chain on the final properties of the copolymers, in the present work we propose to carry out a NMR study with the main aim of determining the values of reactivity ratios in the copolymerization of styrene with a series of di *n*-alkyl and methyl *n*-alkyl

itaconates containing an even number of carbon atoms from 12 up to 22 in the alkyl chain. They were copolymerized at low conversions (<10%) and the reactivity ratios were determined using the Finemann-Ross and Kelen-Tüdös methods [27, 28]. A new treatment which involves the modification of some Kelen-Tüdös parameters was also tried and the results were compared with those obtained by Finemann-Ross and Kelen-Tüdös methods, which are widely used in the determination of the reactivity ratios for great quantity of systems.

## 2. EXPERIMENTAL PART

### 2.1 Materials

Styrene (99.9 %) was dried over CaH<sub>2</sub> and distilled under reduced pressure.

Itaconic acid (Aldrich 99.9 + %) and other chemicals (analytical grade or better) were used without further purification.

### 2.2 Monomer synthesis



Di-*n*-alkyl-itaconates (DI-*n*) were synthesized by esterification of itaconic acid with the corresponding alcohol using *p*-toluenesulfonic acid as catalyst. MeI-*n* were synthesized by methylation of the corresponding mono-*n*-alkyl-itaconates (MI-*n*) with diazomethane following methods previously reported [10, 11].

MI-*n* were prepared essentially in the same way described for DI-*n* using acetyl chloride instead of *p*-toluenesulfonic acid as catalyst [10, 11].

### 2.3 Polymerization

Polymerizations of both series were carried out in bulk at 60°C under nitrogen atmosphere using AIBN (1% molar) during 1 hour, the time required to reach about 5-10% yields. The molar ratio itaconate/styrene in the feed was varied between 4:1 and 1:4. The obtained copolymers were purified by dissolving in chloroform and precipitating with methanol. The purification method was repeated several times. In some cases it was necessary to boil the copolymers with methanol to eliminate the unreacted itaconate. Yields were determined gravimetrically based on the weight of the starting monomers. The nomenclature used for these copolymers is DI-*n*-co-S and MeI-*n*-co-S (X:Y) where *n* is the carbon number of the itaconate side chain and X represents the molar proportion of the itaconate and Y of styrene used in the feed.

In the Figure 1 is shown a scheme of the copolymerization reaction between the diitaconates and methyl itaconates with styrene.

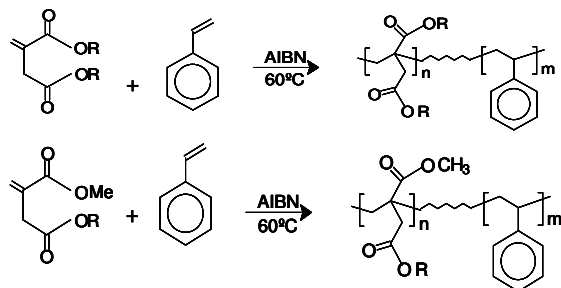

**Figure 1.** Copolymerization reactions between the itaconates and styrene.

### 2.4 Characterization

Infrared spectra were registered on a Fourier Transform Infrared Spectrophotometer (FTIR) Perkin-Elmer System 2000. The samples were prepared on NaCl discs by casting from CHCl<sub>3</sub> solutions.

NMR spectra were recorded on a Bruker AVANCE DRX 400 spectrometer at room temperature from samples dissolved in CDCl<sub>3</sub> using tetramethylsilane (TMS) as internal reference.

### 2.5 Reactivity ratios determination

Reactivity ratios between DI and MeI with styrene in the copolymerization were determined using both the Fineman-Ross (FR) [13] and the Kelen Tüdös (KT) [14] methods. Furthermore, a third new strategy is used for the first time in this paper. The Fineman-Ross equation is:

$$\frac{f(F-1)}{F} = \left(\frac{f^2}{F}\right)r_1 - r_2 \quad (1)$$

Where, *f* is the molar ratio of the monomers in the feed and *F* in the copolymer. Then from the representation of  $f(F-1)/F$  vs  $f^2/F$  it can be obtained *r*<sub>1</sub> and *r*<sub>2</sub> from the slope and the origin.

The Kelen Tüdös equation introduces an arbitrary constant *α* with the aim to separate the data uniformly and at the same time allows that all the points have the same statistical weigh, and is expressed as:

$$\eta = \left(r_1 + \frac{r_2}{\alpha}\right)\xi - \frac{r_2}{\alpha} \quad (2)$$

Where:  $\eta = G/(\alpha + H)$ ,  $\alpha = \sqrt{H_{min} \cdot H_{max}}$ ,  $\xi = H/(\alpha + H)$ ,  $G = f(F-1)/F$ ,  $H = f^2/F$ . As in the former case if is plotted  $\eta$  vs.  $\xi$  the values of *r*<sub>1</sub> y *r*<sub>2</sub> can be obtained from the origin and the slope.

A modification of the KT equation was also used for the determination of the reactivity ratios and was realized by a rearrangement of the copolymer composition equation:

$$F_1 = \frac{r_1 f_1^2 + f_1 f_2}{r_1 f_1^2 + 2f_1 f_2 + r_2 f_2^2} \quad (3)$$

to obtain a new expression where *r*<sub>1</sub> and *r*<sub>2</sub> have the same weigh in the equation:

$$(F_1 - F_2) = \frac{f_1}{f_2} F_2 r_1 - \frac{f_2}{f_1} F_1 r_2 \quad (4)$$

Then we define:

$$(F_1 - F_2) = \beta(r_2 + r_1) + \delta(r_2 - r_1) \quad (5)$$

Where, *β* and *δ* are two arbitrary constants.

Equaling (4) to (5) we obtain,

$$\beta = 1/2(f_1/f_2)F_2 - 1/2(f_2/f_1)F_1 \quad \text{and}$$

$$\delta = -1/2(f_1/f_2)F_2 - 1/2(f_2/f_1)F_1 \quad (6)$$

If equation (5) is used and (*F*<sub>1</sub>-*F*<sub>2</sub>) is plotted vs. *β*, the slope value is (*r*<sub>2</sub>+*r*<sub>1</sub>) and the origin will be  $\delta(r_2-r_1)$ .

Due to the sensibility of *r*<sub>1</sub> and *r*<sub>2</sub> to the mathematical manipulation, the new methodology proposed here, in conjunction with the most classical treatments of FR and KT, provides an additional verification and a statistical support for the values of reactivity ratios reported. The equation works very well as long as the origin  $\delta(r_2-r_1)$  is small.

## 3. RESULTS AND DISCUSSION

### 3.1 Copolymer characterization and compositions determination

Using the reaction conditions described above, both series of copolymers were obtained free of monomer

with yields of about 10% or less. In Tables 1 and 2 are shown the composition of the monomers in the feed and in the copolymer as well as their yields.

The physical appearance of copolymers varies depending on the composition and the length of the side chain of the itaconate units. Then, copolymers constituted by any of the itaconates with 12, 14 or 16 carbon atoms in the side chain and a small quantity of S, were sticky and transparent, but when the amount of S is increased the copolymers become white and gummy. On the other hand, those copolymers composed by itaconates of 18 or 22 carbon atoms in the side chain are white powders and become more rigid as the amount of styrene increase.

FTIR spectra of all of copolymers were similar and exhibit the characteristic bands of both moieties. In Figure 2 are shown as example, the spectra of the series of DI-18-co-S compared with the Poly(di-n-octadecyl itaconate) (PDI-18) and polystyrene (PS).

There it can be seen qualitatively that the most important bands of the styrene moiety, in the region 3100-3000 cm<sup>-1</sup> (stretching =C-H of the aromatic ring), 1602 cm<sup>-1</sup> (symmetric ring stretch), 1500 cm<sup>-1</sup> (ring stretch), 1450 cm<sup>-1</sup> (“sideways” ring stretch) and 760 and 700 cm<sup>-1</sup> (symmetric and no symmetric out-of-plane ring bending), diminish their intensities in comparison with those of the itaconate, as the itaconate ratio increases.

**Table 1.** Monomers molar ratios in the feed, composition of the DI-*n*-co-S copolymers and yields obtained in the copolymerization.

$f_1/f_2$ (I/S) <sup>a</sup>	$F_1/F_2$ (I/S) <sup>b</sup>	Yield (%)	$F_1/F_2$ (I/S) <sup>b</sup>	Yield (%)	$F_1/F_2$ (I/S) <sup>b</sup>	Yield (%)	$F_1/F_2$ (I/S) <sup>b</sup>	Yield (%)	$F_1/F_2$ (I/S) <sup>b</sup>	Yield (%)
DI-12-co-S			DI-14-co-S		DI-16-co-S		DI-18-co-S		DI-22-co-S	
4:1	0.63/0.37	8.4	0.62/0.38	8.4	0.67/0.33	3.4	0.72/0.28	9.4	0.73/0.27	7.9
3:1	0.62/0.38	7.5	0.59/0.41	7.5	0.58/0.42	4.6	0.71/0.29	8.7	0.66/0.34	6.7
2:1	0.61/0.39	6.4	0.57/0.43	6.4	0.56/0.44	6.7	0.60/0.40	6.9	0.61/0.39	9.3
1:1	0.47/0.53	9.0	0.56/0.44	3.0	0.47/0.53	5.5	0.48/0.52	9.8	0.47/0.53	8.6
1:2	0.39/0.61	10.1	0.43/0.57	5.0	0.43/0.57	3.0	0.39/0.61	8.0	0.41/0.59	7.7
1:3	0.34/0.66	8.6	0.36/0.64	9.5	0.37/0.63	6.5	0.33/0.67	10.0	0.38/0.62	10.2
1:4	0.29/0.71	9.5	0.31/0.69	7.2	0.30/0.70	7.6	0.29/0.71	10.1	0.29/0.71	9.1

I: Itaconate, S: Styrene. <sup>a</sup>  $f_1/f_2$  (I/S): Molar fraction of the monomers in the feed. <sup>b</sup>  $F_1/F_2$  (I/S): Copolymers composition measured by <sup>1</sup>H-NMR (expressed in molar ratios).

**Table 2.** Monomers molar ratios in the feed, composition of the MeI-*n*-co-S copolymers and yields obtained in the copolymerization.


$f_1/f_2$ (I/S) <sup>a</sup>	$F_1/F_2$ (I/S) <sup>b</sup>	Yield (%)	$F_1/F_2$ (I/S) <sup>b</sup>	Yield (%)	$F_1/F_2$ (I/S) <sup>b</sup>	Yield (%)	$F_1/F_2$ (I/S) <sup>b</sup>	Yield (%)
MeI-12-co-S		MeI-14-co-S		MeI-16-co-S		MeI-18-co-S		
4:1	0.47/0.53	5.4	0.57/0.43	5.6	-	-	0.63/0.37	6.6
3:1	-	-	0.50/0.50	8.2	0.61/0.39	6.9	0.62/0.38	7.8
2:1	0.41/0.59	6.2	-	-	0.59/0.41	7.8	0.60/0.39	8.5
1:1	-	-	0.44/0.56	7.5	-	-	0.47/0.53	6.5
1:2	0.26/0.74	4.0	0.34/0.66	4.6	0.28/0.72	8.0	-	-
1:3	-	-	0.28/0.72	5.9	0.23/0.77	8.5	0.34/0.66	8.9
1:4	-	-	0.24/0.76	8.2	0.21/0.79	5.4	0.29/0.71	7.7

I: Itaconate, S: Styrene. <sup>a</sup>  $f_1/f_2$  (I/S): Molar fraction of the monomers in the feed. <sup>b</sup>  $F_1/F_2$  (I/S): Copolymers composition measured by <sup>1</sup>H-NMR (expressed in molar ratios).

The NMR spectra obtained from the series of DI-*n*-co-S or MeI-*n*-co-S were similar to each other, and like the FTIR spectra, the intensity of the signals of itaconate and styrene changes as the composition does. Figure 3 shows the  $^1\text{H}$ -NMR spectra of MeI-18 (A) and MeI-18-co-S (1:1) (B) with the respective assignments. In the figure it can be appreciated the spectrum of DI-18-co-S (1:1) (C) for comparison. The signal assignments were confirmed by bidimensional NMR techniques [29].

The composition of the copolymers reported in Table 1 was determined by  $^1\text{H}$ -NMR, comparing the integral of the signals of the  $-\text{CH}_3$  at 0.9 ppm of the side chains of the itaconate (*e* for MeI-18-co-S and *e* and *e'*, for DI-18-co-S) with the aromatic protons of the styrene (*o*, *m*, *p*) (6.30-7.25 ppm). The absence in the copolymers spectra of the two signals

between 5.7 and 6.4 ppm and the triplet at approximately 4.2 ppm corresponding to the  $=\text{CH}_2$  protons and to the  $\text{OCH}_2$  of the side chain of the monomer also indicate that the copolymers were free of monomers. On the other hand, in the spectrum of the MeI-18-co-S (Figure 3B) it may be observed that the signal of  $\text{OCH}_3$  and the  $\text{OCH}_2$ , (*b'*) and (*b*) respectively, are not only shifted in comparison with the corresponding signal of the homopolymer (Figure 3A) [10, 11] but also are highly split in broad signals. This was also observed, although with less intensity for DI-18-co-S (Figure 3C). This fact not only indicates that the copolymerization was successfully carried out, but also suggests that the units of styrene and itaconate are randomly distributed in the copolymer chain.

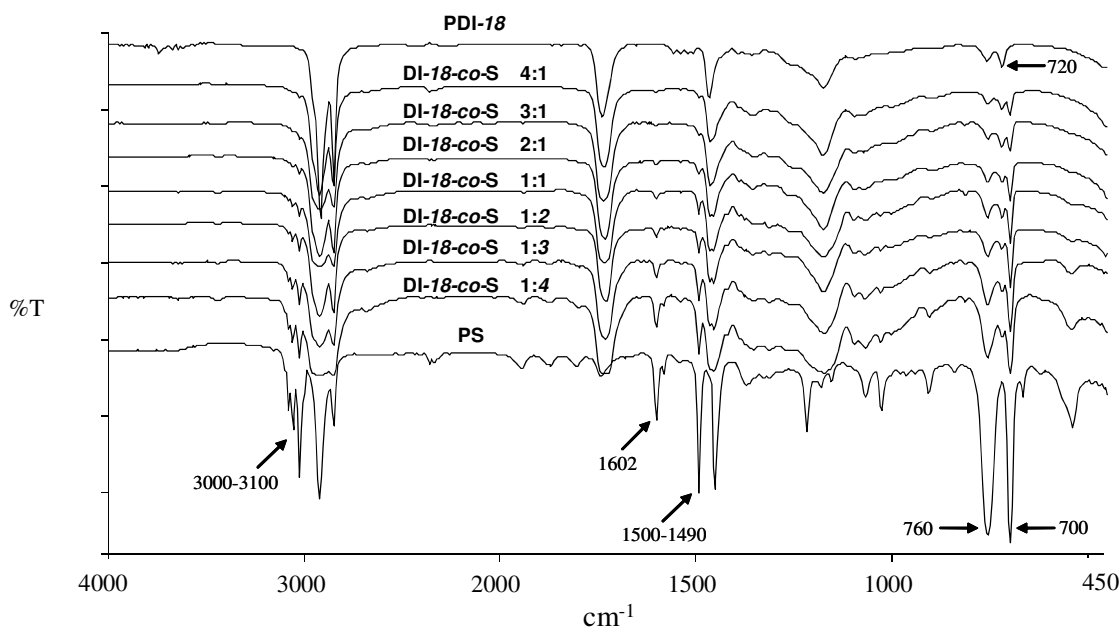

**Figure 2.** FTIR spectra of the series of DI-18-co-S copolymers compared with both homopolymers. Arrows indicate the bands where are observed the most notable changes (see text).

The  $^{13}\text{C}$ -NMR studies confirm the results described above. In Figure 4 The DEPT 135 spectrum of MeI-18-co-S(1:1), which is considered representative of all the series, is compared with polystyrene, and PMeI-18 spectra.

In the copolymer spectrum the signals of the carbons directly attached to the carbonyl groups ( $\text{OCH}_3$  and  $\text{OCH}_2$ ) of the itaconate units (*a* and *e*) are split in several signals and shifted to higher field respect to the signals of the homopolymer. The splitting is due to a change of the chemical

environment produced when an itaconate unit is adjacent to a styrene one, and the shift to upper field is due to the  $\text{OCH}_3$  or  $\text{OCH}_2$  groups of itaconate are located inside of the protection cone of the styrene unit [21, 29]. The methyne carbon of the styrene unit ( $\gamma$ ) also undergo splitting in two signals with a small shifting to higher field, indicating that this signal is also influenced by the itaconate units. The  $^{13}\text{C}$ -NMR of DI-16-co-S exhibits a similar behavior to that described above for MeI-*n*-co-S, although in that case neither the shift nor splits are so noticeable

[21]. The NMR results indicate without any doubt that the structure of these copolymers has mainly random structures. If the obtained products were

alternating or block copolymers the splitting and the shifting of the signals would not be observed.


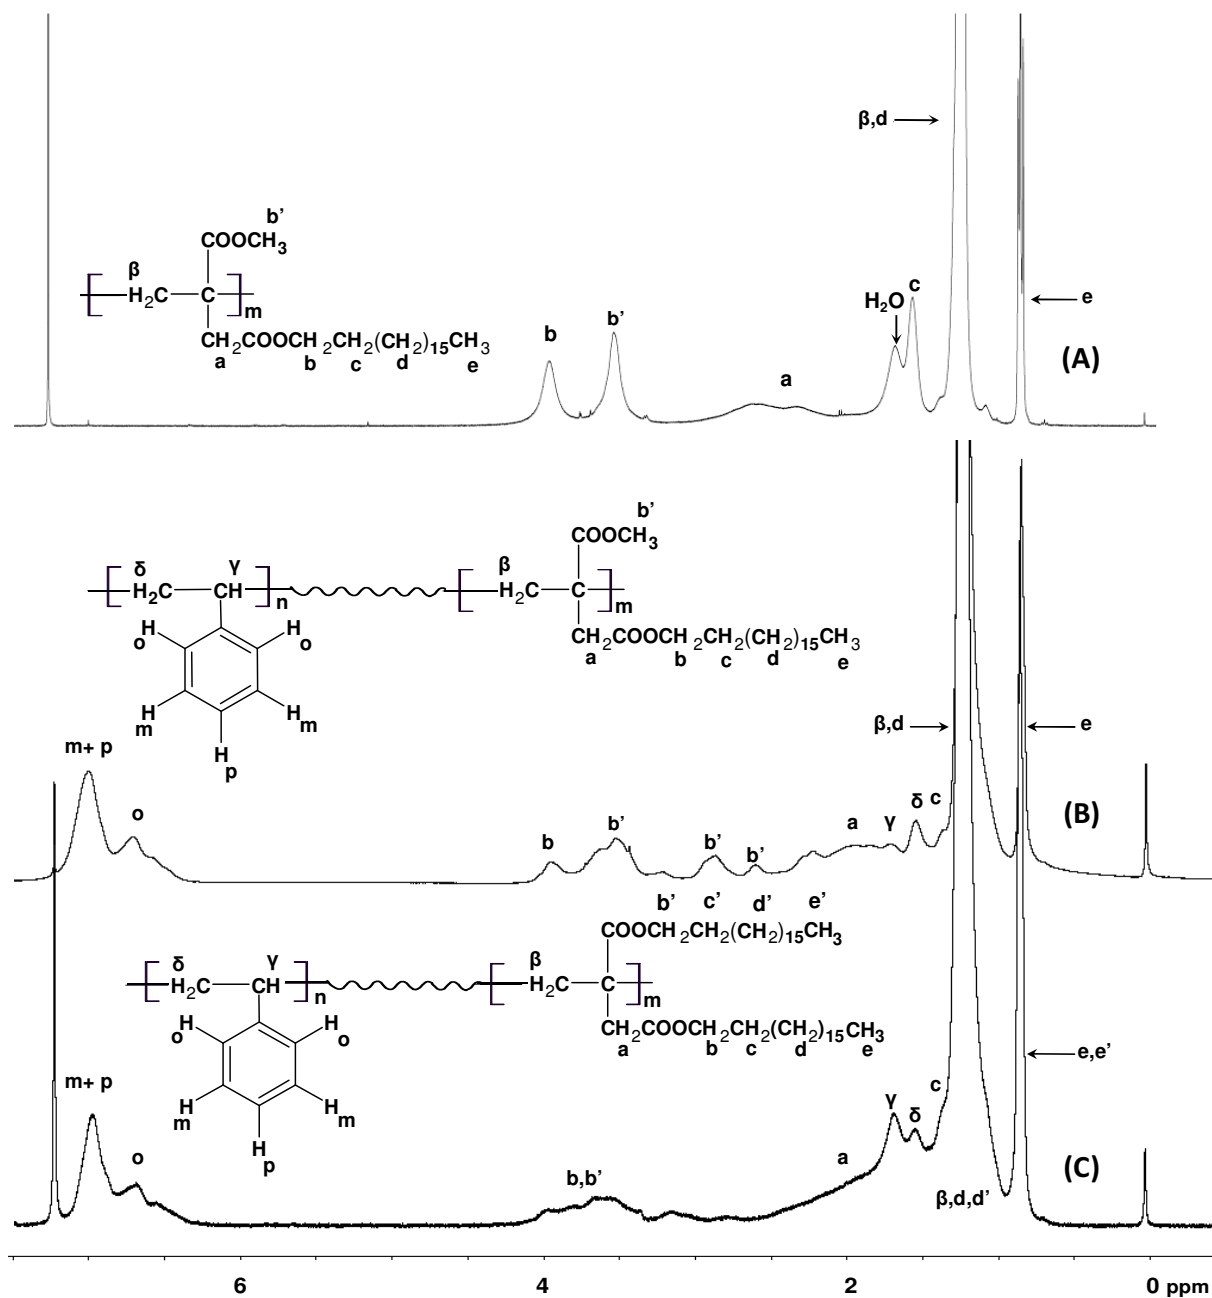


Figure 3. <sup>1</sup>H-NMR spectra in deuterated chloroform of PMeI-18 (A), PMeI-18-co-S (1:1) (B), and PDI 18-co-S (1:1) (C).

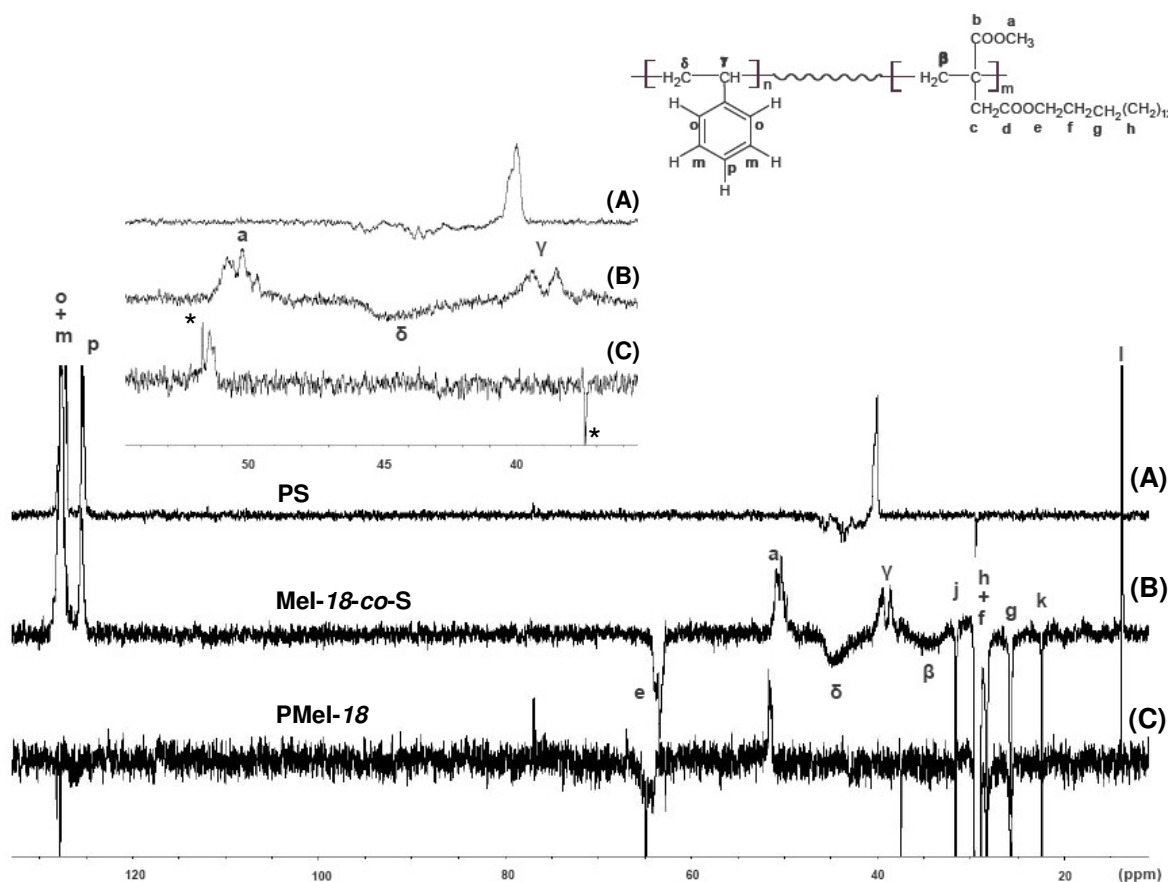

**Figure 4.** DEPT 135 in  $\text{CDCl}_3$  of A) PS, B) MeI-18-co-S(1;1) and C) PMeI-18. The signals labeled with asterisk in C) are small remainder monomer in the homopolymer.

### 3.2 Reactivity ratios determination

The reactivity ratios were determined from the monomer proportion in the feed and the copolymers composition. As mentioned before,  $^1\text{H-NMR}$  was used to quantify the copolymer composition and the FR, KT methods and a modification of the last one were used to determine the reactivity ratios. Reaction times of one hour allow to obtain yields of about 10% or less, which according to the previous report is necessary to apply in these methods [30, 31].

As an example in Figure 5 are shown the plots obtained for the calculated parameters for DI-18-co-S copolymers and in Table 3 the values of  $r_1$  and  $r_2$  for the whole series obtained by the three methods.

As it may be appreciated in Table 3, the obtained values for  $r_1$  and  $r_2$  for each one of the members of DI- $n$ -co-S series were similar for the three methods.

Even more, in all cases is observed that  $r_1$  and  $r_2$  are less than unity and  $0 < r_1 \cdot r_2 < 1$ , indicating that this systems, as in many cases, generate random copolymers but with some tendency to alternation. In the case of the copolymers derivatives from DI-12, 14 and 16,  $r_2$  was slightly higher than  $r_1$ , indicating that styrene units are easier incorporated into the copolymer chain than those of itaconate. While the values for  $r_1$  and  $r_2$  in DI-18 and 22 are closer but with  $r_1$  slightly higher than  $r_2$ .

In the four series of MeI- $n$ -co-S studied here, the values of  $r_2$  were higher than  $r_1$  regardless of the side chain of the itaconate and the difference between  $r_2$  and  $r_1$  for MeI- $n$ -co-S with  $n=12, 14$  and  $16$  was much more pronounced than in the previous cases.

These facts indicate that longest chains in the itaconate, 18 and 22, promote the incorporation of both monomers almost in the same form to the polymer chain, but the shorter ones promote the

preferential incorporation of the styrene. This behavior is more pronounced in the MeI-*n* family as may see in Table 3. At the moment we do not have a satisfactory explanation to this behavior, since nor electronic or steric factor appear to be involved here. More studies must be carried out with others itaconates in order to obtain more conclusive results. Equation (5) could be applied in most cases and the obtained values were similar to those observed with the FR or KT methods, as may be observed in Table

3. However, for the copolymers MeI-12-*co*-S and MeI-14-*co*-S, where there is a markedly difference between the values of  $r_1$  and  $r_2$ , linearity was not observed when this equation is used. This indicates that this equation is only valid when the values of  $r_1$  and  $r_2$  are close and the intercept is small, since this treatment gives equal weight to the variables of the equation. If these values are very different, this treatment is no longer applicable.

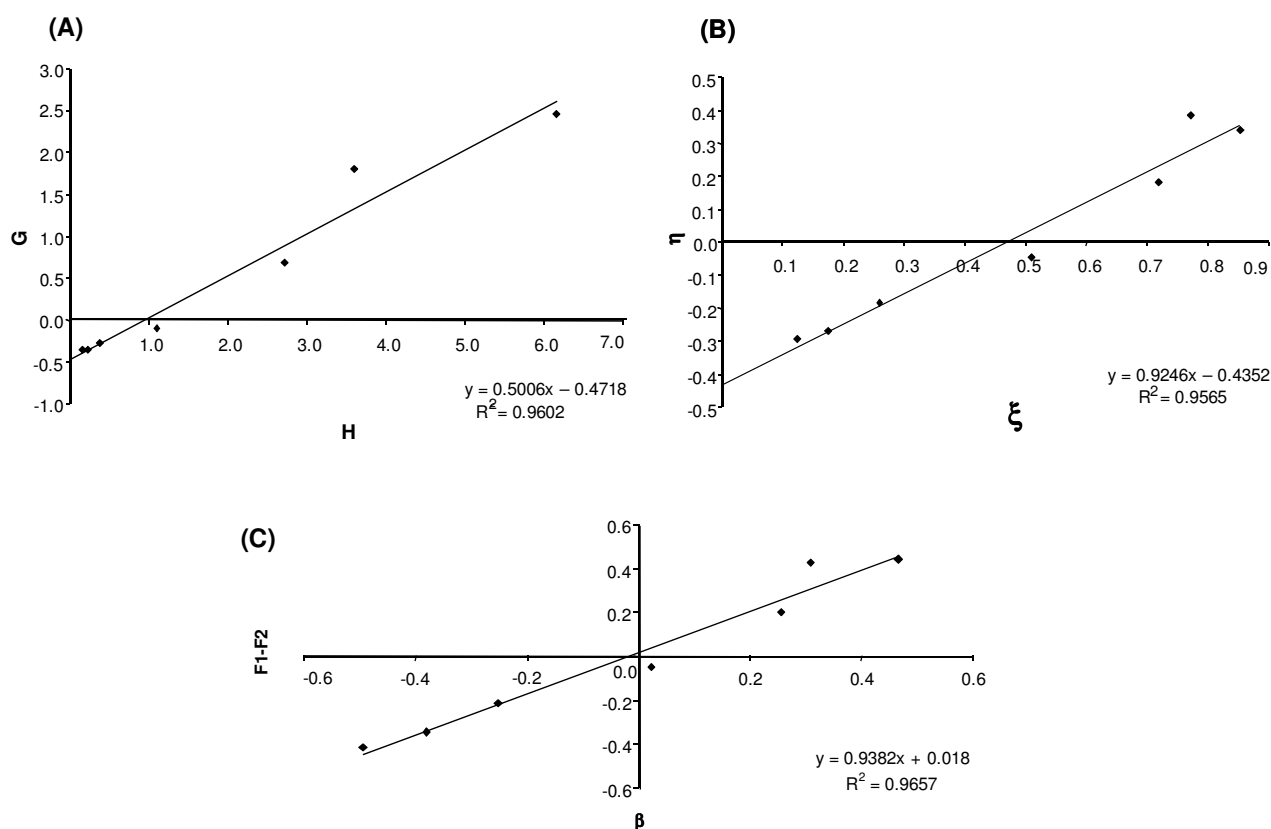


Figure 5. (A) FR (B) KT and (C) modified KT plots for DI-18-*co*-S.

Finally these results indicate that the monomeric units have some tendency to be distributed randomly in the copolymers, which is concordant with the NMR results. At this moment, we are carrying out further work in copolymerization of itaconates with styrene in order to reach more conclusive results related with copolymerization and the structure of these copolymers, and also to evaluate their thermal properties and the effect of styrene on the crystallization of *n*-alkyl side chains of itaconate.

#### 4. CONCLUSIONS

Copolymerization of long side chain DI-*n* and MeI-*n* with S at low conversions provides random copolymers but with some tendency to alternation as was demonstrated by NMR, and confirmed by the methods used for the determination of the reactivity ratios.

In the case of the DI-*n-co*-S copolymers with  $n = 12, 14$  and  $16$  the  $r_{1(D)}$  and  $r_{2(S)}$  values were in the order de 0.2 to 0.3 being those of  $r_{2(S)}$  greater than

**Table 3.** Comparison of the values of reactivity ratios in the copolymerization between *n*-alkylitaconates and S obtained using the three methods.

	DI-12-co-S	DI-14-co-S	DI-16-co-S	DI-18-co-S	DI-22-co-S	MeI-12-co-S	MeI-14-co-S	MeI-16-co-S	MeI-18-co-S
Fineman-Ross									
$r_1$	0.22±0.03	0.19±0.02	0.25±0.04	0.50±0.05	0.46±0.03	0.02±0.01	0.10±0.02	0.38±0.06	0.42±0.03
$r_2$	0.28±0.12	0.18±0.08	0.35±0.16	0.47±0.13	0.44±0.10	0.97±0.07	0.54±0.13	0.84±0.16	0.44±0.10
$R^2$	0.93	0.96	0.90	0.96	0.97	0.93	0.84	0.94	0.98
Kelen Tüdös									
$r_1$	0.28±0.10	0.23±0.16	0.23±0.10	0.49±0.14	0.42±0.13	0.02±0.03	0.10±0.06	0.41±0.22	0.46±0.11
$r_2$	0.39±0.04	0.25±0.06	0.30±0.04	0.46±0.05	0.38±0.05	0.93±0.04	0.53±0.03	0.89±0.09	0.52±0.05
$R^2$	0.95	0.80	0.93	0.96	0.95	0.99	0.97	0.96	0.98
Modified Kelen Tüdös									
$r_1$	0.26±0.05	0.22±0.14	0.23±0.10	0.48±0.13	0.42±0.13	---	---	0.34±0.22	0.45±0.11
$r_2$	0.37±0.05	0.26±0.14	0.31±0.10	0.45±0.13	0.37±0.13	---	---	0.83±0.22	0.51±0.11
$R^2$	0.95	0.86	0.94	0.97	0.95	---	---	0.96	0.98
Average values using all methods									
$r_1$	0.25±0.17	0.21±0.11	0.24±0.08	0.49±0.11	0.43±0.10	0.02±0.02	0.10±0.04	0.38±0.17	0.44±0.08
$r_2$	0.35±0.18	0.23±0.09	0.32±0.10	0.46±0.10	0.40±0.09	0.96±0.05	0.54±0.08	0.85±0.16	0.49±0.09
$r_{1,r_2}$	0.09±0.10	0.05±0.04	0.08±0.05	0.22±0.10	0.17±0.08	0.02±0.02	0.05±0.03	0.32±0.20	0.22±0.08

$r_{1(DI)}$ . These results could be interpreted as a slightly higher incorporation of styrene than itaconate in the copolymer. For the DI-18 and 22, the  $r$  values were between 0.4 and 0.5 and  $r_{1(DI)}$  was slightly higher than  $r_{2(S)}$  indicating in this case a slightly preferential incorporation of the itaconate in the copolymer. However, this interpretation should be taken with some caution since the values are close and the errors are not negligible. Therefore we consider that additional studies must be carried out to reach more conclusive results.

Although for MeI-*n*-co-S the tendencies were more or less the same observed for the diitaconate copolymers, the values of  $r_{2(S)}$  were ever higher than  $r_{1(DI)}$  and their differences increase as the itaconate *n*-alkyl side chain become shorter.

The modification of the KT method carried out in this work and resumed in the equation (5) for the determination of reactivity ratios, showed that it is

only applicable when the values of  $r_1$  and  $r_2$  are too close. This method works satisfactorily when was used in all the DI-*n*-co-S series, but when was used in the copolymerization of MeI-*n* only works adequately when the monomers were MeI-16 and MeI-18.

## 5. ACKNOWLEDGEMENTS

This work has been supported by Consejo de Desarrollo Científico Humanístico y Tecnológico de la Universidad de los Andes, Mérida (Venezuela) (CDCHT-ULA) through the grant C-1517-07-08-A.

## 6. REFERENCES

- [1]. Cowie JMG, Haq C, *Br. Polym. J.* 1977; 9: 241-245.
- [2]. Velickovic J, Filipovic J, *Makromol. Chem.* 1984; 185: 569-578.
- [3]. León A, Gargallo L, Radić D, Horta A, *Polymer* 1991; 32:761-763.

- [4]. Gargallo L, Opazo A, Leiva A, Radić D. *Polymer* 1998; 39: 2069-2072.
- [5]. Boskovic G, Katsikas L, Velickovic J, Popović IG, *Polymer* 2000; 41: 5769-5775.
- [6]. Velada JL, Cesteros C, Madoz A, Katime I. *Macromol. Chem. Phys.* 1995; 196: 3171-3185.
- [7]. Velada JL, Hérnaez E, Cesteros LC, Madoz A, Katime I, *Polym. Degrad. Stab.* 1996; 52: 273-282.
- [8]. Popović IG, Katsikas L, Velicković, *Polym. Degrad. Stab.* 2005; 52: 153-164.
- [9]. Popović IG, Katsikas L, Velicković J, *Polym. Degrad. Stab.* 2005; 89: 165-174.
- [10]. Carrillo M, Martínez de Ilarduya A, Arnal ML, Torres C, López Carrasquero F, *Polym. Bull.* 2002; 48: 59-66.
- [11]. López Carrasquero F, Martínez de Ilarduya A, Cárdenas M, Carrillo M, Arnal ML, Laredo E, Torres C, Méndez B, Müller AJ, *Polymer* 2003; 44: 4969-4979.
- [12]. Madruga EL, Fernández-García M, *Polymer* 1994; 35: 4437-4442.
- [13]. Madruga EL, Fernández-García M *Polym. J.* 1995, 31; 1103-1107.
- [14]. Fernández-García M, Madruga EL, Cuervo-Rodríguez R, *Polymer* 1996; 37:263-268.
- [15]. Fernández-García M, Madruga EL, *Polymer* 1997; 38:1367-1371.
- [16]. Fernández-García M, De la Fuente JL, Madruga EL, *Polym. Eng. Sci.* 2001; 41: 1616-1625.
- [17]. NAKAMURA H, SENO M, TANAKA H, SATO T *MAKROMOL. CHEM.* 1993; 194: 1773-1783.
- [18]. Otsu T, Watanabe H *Eur. Polym. J.* 1993; 29: 167-174.
- [19]. Opazo A, Gargallo L, Radić D, *Polymer Bull.* 1996; 36: 511-516.
- [20]. Inciarte H, Orozco M, Fuenmayor M, López Carrasquero F, Oliva H, *e-Polymers* 2006; 056.
- [21]. Cárdenas MC, Rangel Rangel E, Torres C, López Carrasquero F, *Rev. Iberoam. Poli.* 2008; 9: 222-227.
- [22]. Kumar G, Aggarwal S, Choudhary V, *Indian J. Chem. Section A* 2003; 42 (10): 2523-2526.
- [23]. Kumar G, Aggarwal S, Choudhary V, *Indian J. Chem. Section A* 2004; 43 (2): 278-281.
- [24]. Oishi T, Fujimoto M, *J. Macromol. Sci. Chem.* 1989; A26 (12): 1611-1621.
- [25]. Oishi T, Fujimoto M, *J. Macromol. Sci. Chem.* 1990; A27 (5): 611-623.
- [26]. Petit De Peña Y, López W, Burguera M, Burguera JL, López Carrasquero F, Carrillo M *Anal. Chim. Acta* 2001; 438: 259-266.
- [27]. Finemann F, Ross SD, (). *J. Polym. Sci. Part A: Polym. Chem.* 1950; 5: 259-262.
- [28]. Kelen T, Tüdös F, *J. Macro. Sci. Chem.* 1975; A9: 1.
- [29]. Torres C, Rangel-Rangel E, Cárdenas MC, Koteich-Khatib S, Bahsas A, Laredo E, Dugarte N, López-Carrasquero F, *in preparation*.
- [30]. Patel MV, Dolia MB, Patel JN, Patel RM, *Reactive & Funtional Polymers* 2005; 65: 195-204.
- [31]. O'Leary K, Paul DR, *Polymer* 2004; 45: 6575-6585.